

## Accepted Manuscript

Influence Of Loading Rate, Alkali Fibre Treatment And Crystallinity On Fracture Toughness Of Random Short Hemp Fibre Reinforced Polylactide Bio-composites

Kim L. Pickering, Moyeenuddin A. Sawpan, Jeevan Jayaraman, Alan Fernyhough

PII: S1359-835X(11)00134-5  
DOI: [10.1016/j.compositesa.2011.04.020](https://doi.org/10.1016/j.compositesa.2011.04.020)  
Reference: JCOMA 2877

To appear in: *Composites: Part A*

Received Date: 22 September 2010  
Revised Date: 22 March 2011  
Accepted Date: 26 April 2011

Please cite this article as: Pickering, K.L., Sawpan, M.A., Jayaraman, J., Fernyhough, A., Influence Of Loading Rate, Alkali Fibre Treatment And Crystallinity On Fracture Toughness Of Random Short Hemp Fibre Reinforced Polylactide Bio-composites, *Composites: Part A* (2011), doi: [10.1016/j.compositesa.2011.04.020](https://doi.org/10.1016/j.compositesa.2011.04.020)

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.



1 **Influence Of Loading Rate, Alkali Fibre Treatment And Crystallinity On Fracture**  
2  
3 **Toughness Of Random Short Hemp Fibre Reinforced Polylactide Bio-composites**  
4  
5  
6  
7

8 ***Kim L. Pickering<sup>a</sup>, Moyeenuddin A. Sawpan<sup>b\*</sup>, Jeevan Jayaraman<sup>a</sup> and Alan***  
9 ***Fernyhough<sup>c</sup>***  
10

11  
12 <sup>a</sup> *School of Engineering, University of Waikato, Hamilton, New Zealand*  
13

14  
15 <sup>b</sup> *Composite Materials Research, Pultron Composites Ltd, Gisborne, New Zealand*  
16

17  
18 <sup>c</sup> *Biomaterials Engineering, Biopolymer Network/SCION, Rotorua, New Zealand*  
19  
20  
21

22  
23 **Abstract**  
24

25 Plane-strain fracture toughness ( $K_{Ic}$ ) of random short hemp fibre reinforced polylactide  
26  
27 (PLA) bio-composites was investigated along with the effect of loading rate, fibre  
28  
29 treatment and PLA crystallinity. Fracture toughness testing was carried out at loading  
30  
31 rates varying from 0.5 to 20 mm/min using single-edge-notched bending specimens  
32  
33 with 0 to 30 wt% fibre.  $K_Q$  (trial  $K_{Ic}$ ) of composites decreased as loading rate  
34  
35 increased, until stabilising to give  $K_{Ic}$  values at a loading rate of 10 mm/min and  
36  
37 higher. The reduction of crazing and stress whitening, as well as a more direct crack  
38  
39 path observed in PLA samples combined with reduced plastic deformation observed in  
40  
41 composites provided explanation for this reduction.  $K_{Ic}$  of composites was found to  
42  
43 decrease with increased fibre content and fibre treatment with sodium hydroxide.  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

Studies controlling the degree of PLA crystallinity by heat treatment or “annealing”  
showed that reduction of  $K_{Ic}$  can be attributed to increased crystallinity.

1 Key words: A. Polymer-matrix composites (PMCs); A. Fibres; B. Fracture toughness;

2  
3 D. Fractography  
4  
5  
6  
7

8 \* Corresponding author.  
9

10 E-mail: moyeen@pultron.com; Tel: +64 6 867 8582; Fax: +64 6 867 8542  
11  
12  
13  
14  
15

## 16 **1. Introduction**

17  
18 In recent years, bio-based composite materials have been the focus of academic and  
19  
20 industrial research interest from the viewpoint of reducing impact on the natural  
21  
22 environment [1]. Polylactide (PLA) is considered one of the most promising renewable  
23  
24 resource based biopolymer matrices. This is because the physical and mechanical  
25  
26 properties of PLA make it a good alternative to currently used commodity polymers  
27  
28 such as polypropylene and poly(ethylene terephthalate) and it is readily fabricated to  
29  
30 produce injection moulded parts, film, or fibres [2, 3].  
31  
32  
33  
34  
35  
36

37  
38 For structural application, there is a need to better understand and describe the fracture  
39  
40 behaviour of PLA. Fracture toughness of a given material is a function of testing speed  
41  
42 and temperature [4] and so assessment of rate dependent fracture mechanisms is  
43

44 important for the designer in understanding mechanical performance of composites [5].  
45

46  
47 Reduction of fracture toughness with increased testing rate has been observed for  
48  
49 polymers including PLA [5-7] and has been associated with the reduction of crazing and  
50  
51 plastic blunting at the crack tip for higher loading rates corresponding to the reduction  
52  
53 of energy dissipation. Although many research works have reported the influence of  
54  
55 loading rate on fracture toughness of synthetic fibre reinforced composites [6-9], the  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 vast majority of these are based on continuous fibre composites, although increasingly  
2 brittle behaviour has been reported with short glass fibres at higher loading rates.

3  
4  
5 Interfacial strength and mechanical properties such as tensile, flexural, impact, creep  
6 and fatigue of natural fibre reinforced bio-composites have been reported by other  
7  
8  
9 researchers [10-14]. However, there is no literature on the effects of loading rate on  
10  
11  
12 fracture toughness of short natural fibre reinforced bio-composites, which have high  
13  
14  
15 potential in load bearing engineering applications.  
16  
17

18  
19  
20 When natural fibres are used as a reinforcing material in semicrystalline polymer  
21  
22 matrices such as PLA, they can act as nucleating sites for crystal growth and commonly  
23  
24 a transcrystalline layer grows from the crystalline cellulose surfaces [1, 15, 16] which is  
25  
26 likely to influence fracture. Previous studies [17, 18] demonstrated that reinforcing  
27  
28 hemp fibre increases the tensile strength, Young's modulus, impact strength and  
29  
30 flexural modulus of PLA bio-composites which is a good indication of compatibility of  
31  
32  
33 hemp fibre with PLA. The objective of this work was to investigate fracture toughness  
34  
35  
36 of random short hemp fibre reinforced PLA bio-composites over a range of loading  
37  
38  
39 rates, fibre contents, and different levels of matrix crystallinity along with the effect of  
40  
41  
42 fibre treatment to elucidate important factors influencing this parameter.  
43  
44

## 45 **2. Experimental**

### 46 *2.1. Materials*

47  
48 NatureWorks<sup>®</sup> PLA (polylactide) polymer 4042D, from NatureWorks LLC, USA, was  
49  
50 used as a matrix. This was provided in a pellet form with a density of 1.25 g/cc. Retted  
51  
52  
53 hemp bast fibre was supplied by Hemcore, UK. The average length and diameter of the  
54  
55  
56 fibre were 65mm and 31.5 $\mu$ m, respectively.  
57  
58  
59  
60  
61  
62  
63  
64  
65

## 2.2. Fibre Treatment

Fibres were washed with hot water (50°C) to remove dirt and impurities, dried and then soaked in 5 wt% sodium hydroxide (NaOH) solution at ambient temperature, maintaining a fibre:solution ratio of 20:1 (by weight). The fibres were immersed in the solution for 30 min. After treatment, fibres were copiously washed with water and subsequently neutralised with 1 wt% acetic acid solution. The treated fibres were then dried in an oven at 80°C for 48 h. The average diameter of the fibres was decreased to 25.8µm after treatment due to the removal of external impurities (e.g. wax).

## 2.3. Cellulose crystallinity index

Approximately 15 mg of fibres were cut and pressed into a disk using a cylindrical steel mould with an applied pressure of 10 MPa in laboratory hydraulic press. Cellulose crystallinity index ( $I_{XRD}$ ) was calculated by means of the Segal equation as follows [19, 20]:

$$I_{XRD} (\%) = \frac{I_{002} - I_{amp}}{I_{002}} * 100 \quad (1)$$

where  $I_{002}$  is the maximum intensity of the 002 lattice diffraction plane at an angle  $2\theta$  of between 22° and 23° ( $22^\circ \leq 2\theta \leq 23^\circ$ ) and  $I_{amp}$  is the intensity diffraction at an angle  $2\theta$  close to 18° representing amorphous materials in cellulosic fibres.

## 2.4. Interfacial strength measurement

For pull-out specimen preparation, a hole of 6 mm diameter was made in a silicone rubber mould (18mm x 24mm x 3 mm) positioned relatively central and near to one of the two longest sides using a punch (see Fig. 1). A slot was cut to a depth of 2.5 mm to give a channel from the outer wall of the mould to the punched hole. The mould was flexed to open the cut to allow the introduction of a fibre and then released to grip the

1 fibre. The desired embedded length was obtained by drawing the fibre through the cut  
2  
3 under optical light microscope. Fibre diameters were measured using an optical  
4  
5 microscope with a calibrated eye-piece. Then the mould was placed on a piece of  
6  
7 polytetrafluoroethylene (PTFE) sheet on a glass plate, and two small pieces from a PLA  
8  
9 pellet were placed into the mould cavity. This was then placed in a pre-heated oven  
10  
11 (180°C) for 5 min and then allowed to cool in air at room temperature. Samples were  
12  
13 prepared with a range of embedded lengths from 0.25 mm to 2 mm with a free-fibre  
14  
15 length of approximately 5 mm. The free-fibre end was glued to a piece of cardboard.  
16  
17 Pull-out testing was performed on an Instron 4204 Universal Testing machine. The  
18  
19 sample was gripped at the upper cross-head and the paper cardboard was gripped by the  
20  
21 stationary bottom part. The force was measured with an accuracy of  $\pm 0.1$  mN.  
22  
23

24 Interfacial strength ( $\tau_{po}$ ) was calculated using the following equation [10, 21]:  
25  
26

$$\tau_{po} = \frac{F_{max}}{\pi d l_e} \quad (2)$$

27 where  $F_{max}$  is the maximum load,  $d$  is the fibre diameter and  $l_e$  is the embedded length.  
28  
29

### 30 2.5. Single Fibre Testing

31 Single fibre tensile strength of hemp fibres was measured according to the ASTM  
32  
33 D3379-75 Standard Test Method for Tensile Strength and Young's Modulus for High-  
34  
35 Modulus Single Filament Materials [22]. Specimens were prepared by separating fibre  
36  
37 bundles by hand, and then attaching single fibres to cardboard mounting-cards using  
38  
39 polyvinyl acetate glue with 10 mm holes punched into them to give a gauge length of 10  
40  
41 mm. The mounted fibres were then placed in the grips of an Instron 4204 tensile testing  
42  
43 machine, and a hot-wire cutter was used to cut the supporting sides of the mounting  
44  
45 cards.  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57

### 58 2.6. Composite Processing

Hemp fibres (average length 4.9 mm) were initially washed with hot water and the fibre and PLA were dried in an oven at 80°C overnight. PLA/hemp fibre composites were compounded (10, 15, 20 and 30 wt% fibre) in a ThermoPrism TSE-16-TC twin screw extruder. The extruder barrel consisted of 5 heating zones, which were set at 110°C, 130°C, 180°C, 190°C, and 185°C from feed zone to die exit. The screw diameter was 15.6mm and the co-rotating screws were operated at 100 rpm. The extruded composite material was pelletised and dried at 80°C for 24 h and then injection moulded using a BOY15-S injection moulding machine. The feeding, compression and metering sections of the injection moulding machine were set at 155 °C, 180 °C and 190°C, respectively. The injection screw speed was set at 160 rpm. Fibre length distribution and fibre diameter of the composites are available elsewhere [23].

### 2.7. Composite Annealing

Alkali treated fibre composite samples were heat treated or “annealed” at 70°C and 100°C (above glass transition temperature of PLA (i.e. 57.8°C)) for 3, 8 and 24 h in an oven.

### 2.8. Differential scanning calorimetry (DSC)

DSC scans were carried out at a scan rate of 10°C/min from room temperature to 200°C in the presence of air using samples of approximately 10 mg to assess the influence of fibre content and fibre treatment on the crystallinity of PLA. The crystallinity ( $X_{DSC}$ ) of PLA was calculated using the following equation [16]:

$$X_{DSC}(\%) = \frac{\Delta H_f - \Delta H_{cc}}{\Delta H_f^o} \times \frac{100}{w} \quad (3)$$

where  $\Delta H_f^o = 93$  J/g for 100% crystalline PLA,  $\Delta H_f$  is the enthalpy of melting,  $\Delta H_{cc}$  is the cold crystallisation enthalpy and  $w$  is the weight fraction of PLA in the composite.

## 2.9. Fracture toughness testing

Fracture toughness testing was carried out using single-edge-notched bend (SENB) specimens according to the ASTM D 5045-99 Standard Test Methods for Plane-Strain Fracture Toughness and Strain Energy Release Rate of Plastic Materials. The length (L), span length (S), width (W) and thickness (B) of the specimens were 126, 56, 12.7 ( $\pm 0.03$ ) and 3.5 ( $\pm 0.03$ ) mm respectively, which satisfies the condition  $2B < W < 4B$  as specified in the standard. The initial crack length ( $a$ ) was 6.35 mm ( $\pm 0.005$ ). The loading speed was varied from 0.5 mm/min to 20 mm/min and the notch root of the specimens was sharpened using a razor blade before testing. Four replicate specimens were tested. Mode I plane-strain fracture toughness ( $K_{Ic}$ ) of single-edge-notch-bending (SENB) specimens was calculated with the following relationships [4]:

$$K_Q = \left( \frac{P_Q}{BW^{1/2}} \right) f(x) \quad (4)$$

where  $K_Q$ ,  $P_Q$ ,  $B$  and  $W$  are trial  $K_{Ic}$ , maximum load, specimen thickness and width, respectively,

$$\text{and } f(x) = 6x^{1/2} \frac{[1.99 - x(1-x)(2.15 - 3.93x + 2.7x^2)]}{(1+2x)(1-x)^{3/2}} \quad (5)$$

such that  $x = a/W$ , where  $a$  is the initial crack length. In order for  $K_Q$  to be considered the plane-strain fracture toughness,  $K_{Ic}$ , the following size criterion must be satisfied:

$$B, a, (W - a) > 2.5(K_Q / \sigma_t)^2 \quad (6)$$

where  $\sigma_t$  is the tensile strength obtained from tensile testing performed based on ASTM D 638 Test Method for Tensile Properties of Plastics [24] with loading rate and



1 temperature the same as for fracture toughness testing. Four samples were tested for  
2  
3 each batch of samples.  
4

#### 5 6 *2.10. Light microscopy*

7  
8 To allow for visual inspection of crystallinity, single fibre samples were prepared by  
9  
10 embedding a hemp fibre in molten PLA between two slides and squeezing the slides  
11  
12 together. Then the sample was allowed to cool down to room temperature to allow  
13  
14 solidification of the PLA then inspected. Fracture surfaces were also inspected using an  
15  
16 Olympus BX60F5 optical light microscope and a WILD M3B stereo microscope.  
17  
18 Micrographs were obtained using a Nikon camera (Digital Sight DS-U1).  
19  
20  
21

### 22 23 **3. Results and Discussion**

#### 24 25 *3.1 Effect of Fibre Treatment on Single Fibre Properties and Interfacial Shear Strength*

26  
27 Crystallinity index of fibres was found to increase compared with untreated fibres  
28  
29 (91.6% compared with 87.9%). This is likely to be due to removal of amorphous  
30  
31 components allowing better alignment of cellulose chains as observed elsewhere [25].  
32  
33 This correlated with an increase in average fibre tensile strength (from 577 to 598 MPa),  
34  
35 although this increase was found to not be statistically significant. Interfacial shear  
36  
37 strength (IFSS) of the PLA/hemp fibre samples as a function of fibre embedded length  
38  
39 is depicted in Fig. 2. The non-linear relationship between these two parameters is  
40  
41 indicative of a brittle-like interface fracture as reported in the literature [26] such that  
42  
43 catastrophic failure occurs once a critical crack length is achieved. Average interfacial  
44  
45 shear strengths increased from 5.55 MPa for untreated fibre to 11.41 MPa for alkali  
46  
47 treated fibres, which is likely to be due to the removal of non-cellulosic material  
48  
49 allowing stronger bonding between PLA and cellulose at the interface.  
50  
51  
52  
53  
54  
55  
56

#### 57 *3.2. Effect of Fibre Content and Fibre Treatment on PLA Crystallinity*

1 PLA crystallinity in composites was found to increase with fibre content, which is in  
2  
3 agreement with findings in the literature [16], as well as with fibre treatment as shown  
4  
5 in Fig. 3, suggesting that the fibre acts as a nucleating agent which is more effective  
6  
7 when more crystalline cellulose is exposed. Fig. 4 shows a single untreated fibre  
8  
9 composite sample exhibiting crystallinity including spherulites in the PLA as well as  
10  
11 transcrystallinity at the fibre/matrix interface further supporting that the fibre acts as a  
12  
13 nucleating agent. The amount of transcrystallinity was observed to increase with fibre  
14  
15 treatment (see Fig. 5).  
16  
17  
18  
19

### 20 *3.3. Fracture Toughness Testing*

#### 21 *Load-displacement behaviour*

22  
23  
24  
25 Typical load-displacement graphs for PLA and composites under various loading rates  
26  
27 are depicted in Fig. 6. It may be observed that these showed initially linear deformation,  
28  
29 followed by an amount of non-linear deformation prior to the attainment of maximum  
30  
31 load. Once the maximum load was attained, the recorded load diminished gradually  
32  
33 which was most probably a result of cracking along with limited plastic deformation. It  
34  
35 can be easily seen that the curves became steeper with increased fibre content. This  
36  
37 behaviour was expected because the Young's modulus of the hemp fibre is superior to  
38  
39 that of PLA. It is also evident that the area under the curves decreased with increased  
40  
41 loading rate. This observation is attributed to decreased plastic deformation at higher  
42  
43 loading rates.  
44  
45  
46  
47  
48  
49  
50  
51

52 As can be seen clearly in Fig. 7, if a line (AC) is drawn with a gradient of 5% less than  
53  
54 that of the tangent (AB) to the original loading line, the recorded maximum load ( $P_{\max}$ ),  
55  
56 lies between these two lines, which thus meets the requirement of the standard [4] for  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 allowance of  $P_{\max}$  to be used as  $P_Q$  for the calculations of  $K_Q$  (see Eq. 4). This form of  
2  
3  
4 load-displacement behaviour was observed for all the samples tested.

### 6 *Effect of loading rate and fibre content*

7  
8 The tensile strength of PLA and composites for two different loading rates is  
9  
10 summarised in Table 1. The tensile strength was found to increase with fibre content  
11  
12 and was higher at higher testing speeds which would be expected due to less time for  
13  
14 thermal fluctuations within the material to assist with molecular flow. Further details of  
15  
16 tensile properties including stress-strain curves and Young's modulus are given  
17  
18 elsewhere [17]. Fig. 8 illustrates  $K_Q$  of PLA and composites as a function of loading  
19  
20 rate. It can be seen that  $K_Q$  for all fibre contents decreased with increased loading rate  
21  
22 up to 10mm/min above which it stabilised at a constant value. It was found (using Eq.  
23  
24 6) that at a loading rate of 5 mm/min,  $K_Q$  of the matrix and composites did not satisfy  
25  
26 plane strain conditions. On the other hand,  $K_Q$  at a loading speed of 10 mm/min was  
27  
28 found to fulfil the required criteria given in Eq. 6 and therefore be equivalent to  $K_{Ic}$ .  
29  
30 Since the magnitude of  $K_Q$  from 10 mm/min to higher loading rates was approximately  
31  
32 constant, and given the general expectation of increased yield strength with increased  
33  
34 loading rate, it is likely that the criterion of Eq. 6 was also met for the higher loading  
35  
36 rates above 10 mm/min.  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49

50 Also from Fig. 8, it is evident that  $K_Q$  of the PLA/hemp composites decreased with  
51  
52 increased fibre content. One possible influence is the stress concentration due to the  
53  
54 presence of fibres. However, research elsewhere on PLA [27], has shown the reduction  
55  
56 of fracture toughness with increased crystallinity which could be a factor here. Fig. 9  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 presents DSC traces from which PLA crystallinity values were calculated (as well as  
2 depicting the glass transition point and cold crystallisation and melting peaks) and Fig.  
3  
4 10 shows the relationship of composite  $K_{Ic}$  and PLA crystallinity obtained at different  
5  
6 fibre contents, which demonstrates a convincing trend of decreasing  $K_{Ic}$  with increased  
7  
8 crystallinity.  
9  
10  
11  
12

### 13 *Fractography of PLA and composites*

14  
15  
16 Light micrographs of cracks (side view) of the PLA samples tested under different  
17  
18 loading rates are shown in Fig. 11. As can be seen, extensive crazing was generated in  
19  
20 the crack-tip region for samples tested at lower loading rates (1 and 5 mm/min), but not  
21  
22 so apparent at higher loading rates (including 10 mm/min).  
23  
24  
25  
26  
27

28  
29 Typical fracture surfaces of PLA investigated for a range of loading rates are presented  
30  
31 in Fig. 12. The fracture surfaces showed two distinct zones, namely a smooth zone  
32  
33 suggesting brittle-like fracture next to the initial starter notch and a stress-whitened zone  
34  
35 associated with crazing. A reduction in the stress-whitened region and increase in size  
36  
37 of the smooth brittle-like region further supported that at higher loading rates crack  
38  
39 propagation involved less crazing leading to lower  $K_Q$  values.  
40  
41  
42  
43  
44  
45

46  
47 Typical crack paths of PLA/hemp composites (side view) tested at 5 mm/min and  
48  
49 10mm/min are presented in Figs. 13 and 14, respectively. As can be seen, cracks were  
50  
51 initiated from the tip of the pre-existing crack, but did not propagate directly across the  
52  
53 sample and appear to have been influenced by the presence of fibres such that increased  
54  
55 fibre volume fraction resulted in a more irregular crack path. Within the composites  
56  
57 tested at 5 mm/min (Fig. 13), evidence of localised matrix tearing is present suggesting  
58  
59  
60  
61  
62  
63  
64  
65

1 limited plastic deformation. A closer examination of the crack propagation path  
2  
3 indicates that the two fracture surfaces were not completely separated, but rather  
4  
5 connected by the deformed matrix. This behaviour was commonly observed for all the  
6  
7 samples at lower loading rates, irrespective of the amount of fibre content. There was a  
8  
9 significant reduction in the plastic flow and/or matrix tearing when the samples were  
10  
11 tested at 10 mm/min (Fig. 14) which could explain the reduction of  $K_Q$  at higher  
12  
13 loading rates. In contrast to lower loading rates, the two fracture surfaces were  
14  
15 completely separated ahead of the starter crack.  
16  
17  
18  
19  
20

### 21 *Effect of Fibre Treatment*

22  
23 Fig. 15 presents a comparison of  $K_{Ic}$  values obtained at a rate of 10mm/min for  
24  
25 untreated and treated fibre composites at different fibre contents. These composites  
26  
27 were made from a more recently procured batch of fibre than earlier experiments, which  
28  
29 explains the slight differences for untreated fibres values compared to those in Fig. 8.  
30  
31

32  
33  $K_{Ic}$  values for treated fibre composites followed the same trend of reduction with  
34  
35 increased fibre content as for untreated fibre composites, but were lower. This could  
36  
37 have been due to improved interfacial bonding leading to easier crack propagation,  
38  
39 although it has been seen that crystallinity increases with fibre treatment and again as  
40  
41 for increased fibre content could be playing a role in reduced  $K_{Ic}$ .  
42  
43  
44  
45

### 46 *Effect of annealing on PLA Crystallinity*

47  
48 Fig. 16 shows the effect of heat treating or “annealing” treated fibre composites for  
49  
50 different times at different temperatures on PLA crystallinity conducted in order to  
51  
52 isolate its effect on  $K_{Ic}$ . The crystallinity for the control PLA samples was around 3%.  
53  
54 This increased slightly with the presence of fibre. Only limited increase in crystallinity  
55  
56 was observed for 3 h at 70°C. On increased duration of annealing at 70°C, PLA only  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 samples were relatively unaffected whereas composites were seen to undergo a  
2  
3 significant increase in crystallinity, supporting that hemp fibre acts as a nucleating  
4  
5 agent. Further increases were seen when annealing at 100°C for 24 h (close to the cold  
6  
7 crystallinity peak temperature for PLA) was carried out, where crystallinity reached up  
8  
9 to approximately 35% for PLA and up to 51% for composites of 15 wt% fibre. The  
10  
11 effect of crystallinity on  $K_{Ic}$  is presented in Fig. 17. The trend lines show a reduction of  
12  
13  $K_{Ic}$  for PLA and composites as crystallinity increased, although there is not a clear  
14  
15 trend between the two different fibre contents.  
16  
17  
18  
19  
20

#### 21 **4. Conclusions**

22  
23 In this work,  $K_Q$  of random short hemp fibre reinforced PLA bio-composites was found  
24  
25 to decrease with increased loading rate until plane strain conditions were met at  
26  
27 10mm/min and above.  $K_{Ic}$  was found to decrease with increased fibre content and fibre  
28  
29 treatment coinciding with an increase in crystallinity. Heat treatments conducted to  
30  
31 isolate the effect of crystallinity showed that  $K_{Ic}$  is reduced by increased crystallinity,  
32  
33 suggesting that transcrystallinity within the composites is having a large influence on  
34  
35 the fracture behaviour of composites and may serve as an easy path for crack  
36  
37 propagation. However, increased stress concentration with increased fibre content and  
38  
39 increased interfacial strength with treatment may also be contributing to reduction of  
40  
41  $K_{Ic}$  for composites. It is concluded that it is possible to improve fracture toughness of  
42  
43 this type of composite by controlling crystallinity during composite production.  
44  
45  
46  
47  
48  
49  
50

#### 51 **Acknowledgement**

52  
53 Financial support from Biopolymer Network Ltd, New Zealand is gratefully  
54  
55 acknowledged.  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

**References**

- [1] R. Masirek, Z. Kulinski, D. Chionna, E. Piorkowska, and M. Pracella, Composites of poly(L-lactide) with hemp fibers: Morphology and thermal and mechanical properties, *Journal of Applied Polymer Science* 105 (2007) 255-268.
- [2] D. Plackett, T. L. Andersen, W. B. Pedersen, and L. Nielsen, Biodegradable composites based on L-poly(lactide) and jute fibres, *Composites Science and Technology* 63 (2003) 1287-1296.
- [3] S. Serizawa, K. Inoue, and M. Iji, Kenaf-fiber-reinforced poly(lactic acid) used for electronic products, *Journal of Applied Polymer Science* 100 (2006) 618-624.
- [4] Standard Test Methods for Plane-Strain Fracture Toughness and Strain Energy Release Rate of Plastic Materials, ASTM D 5045 (1999).
- [5] R. Gensler, C. J. G. Plummer, C. Grein, and H. H. Kaysch, Influence of the loading rate on the fracture resistance of isotactic polypropylene and impact modified isotactic polypropylene, *Polymer* 41 (2000) 3809-3819.
- [6] G. C. Jacob, J. M. Starbuck, J. F. Fellers, S. Simunovic, and R. G. Boeman, Fracture toughness in random-chopped fiber-reinforced composites and their strain rate dependence, *Journal of Applied Polymer Science* 100 (2006) 695-701.
- [7] J. W. Gillespie, L. A. Carlsson, and A. J. Smiley, Rate-dependent mode I interlaminar crack growth mechanisms in graphite/epoxy and graphite/PEEK, *Composites Science and Technology* 28 (1987) 1-15.
- [8] I. Levay, G. B. Lenkey, L. Toth, and Z. Major, The effect of the testing conditions on the fracture mechanics characteristics of short glass fibre reinforced polyamide, *Journal of Materials Processing Technology* 133 (2003) 143-148.

- 1 [9] J. Karger-Kocsis, and K. Friedrich, Temperature and strain-rate effects on the  
2 fracture toughness of poly(ether ether ketone) and its short glass-fibre reinforced  
3 composite, *Polymer* 27 (1986) 1753-1760.  
4  
5  
6  
7  
8 [10] S. Wong, R. A. Shanks, and A. Hodzic, Effect of additives on the interfacial  
9 strength of poly(L-lactic acid) and poly(3-hydroxy butyric acid)-flax fibre composites,  
10 *Composites Science and Technology* 67 (2007) 2478-2484.  
11  
12  
13  
14 [11] R. Tokoro, D. M. Vu, K. Okubo, T. Tanaka, T. Fujii, and T. Fujiura, How to  
15 improve mechanical properties of polylactic acid with bamboo fibers, *Journal of*  
16 *Materials Science* 43 (2008) 775-787.  
17  
18  
19  
20  
21 [12] B. Bax, and J. Mussig, Impact and tensile properties of PLA/Cordenka and  
22 PLA/flax composites, *Composites Science and Technology* 68 (2008) 1601-1607.  
23  
24  
25  
26 [13] S. Wong, and R. A. Shanks, Creep behaviour of biopolymers and modified flax  
27 fibre composites, *Composite Interfaces* 15 (2008) 131-145.  
28  
29  
30  
31 [14] S. Wong, R. A. Shanks, and A. Hodzic, Mechanical behavior and fracture  
32 toughness of poly(L-lactic acid)-natural fiber composites modified with hyperbranched  
33 polymers, *Macromolecular Materials and Engineering* 289 (2004) 447.  
34  
35  
36  
37 [15] A. P. Mathew, K. Oksman, and M. Sain, The effect of morphology and chemical  
38 characteristics of cellulose reinforcements on the crystallinity of polylactic acid, *Journal*  
39 *of Applied Polymer Science* 101 (2006) 300-310.  
40  
41  
42  
43 [16] S. Pilla, S. Gong, E. O'Neill, R. M. Rowell, and A. M. Krzysik, Polylactide-pine  
44 wood flour composites, *Polymer Engineering and Science* 48 (2008) 578-587.  
45  
46  
47  
48 [17] M. A. Sawpan, K. L. Pickering, and A. Fernyhough, Improvement of mechanical  
49 performance of industrial hemp fibre reinforced polylactide biocomposites, *Composites*  
50 *Part A: Applied Science and Manufacturing* 42 (2011) 310-319.  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



- 1 [18] M. A. Sawpan, K. L. Pickering, and A. Fernyhough, Characterisation of hemp fibre  
2 reinforced Poly(Lactic Acid) composites, International Journal Materials and Product  
3 Technology 36 (2009) 229-240.  
4  
5  
6  
7  
8 [19] L. Y. Mwaikambo, and M. P. Ansell, Chemical modification of hemp, sisal, jute,  
9 and kapok fibers by alkalization, Journal of Applied Polymer Science 84 (2002) 2222-  
10 2234.  
11  
12  
13  
14  
15 [20] M. Le Troedec, D. Sedan, C. Peyratout, J. P. Bonnet, A. Smith, R. Guinebretiere,  
16 V. Gloaguen, and P. Krausz, Influence of various chemical treatments on the  
17 composition and structure of hemp fibres, Composites Part A: Applied Science and  
18 Manufacturing 39 (2008) 514-522.  
19  
20  
21  
22  
23 [21] S. Zhandarov, and E. Mader, Characterization of fiber/matrix interface strength:  
24 applicability of different tests, approaches and parameters, Composites Science and  
25 Technology 65 (2005) 149-160.  
26  
27  
28  
29  
30  
31  
32 [22] Standard Test Method for Tensile Strength and Young's Modulus for High-  
33 Modulus Single-Filament Materials, ASTM D 3379 (1989).  
34  
35  
36  
37 [23] M. A. Sawpan, Mechanical Performance of Industrial Hemp Fibre Reinforced  
38 Polylactide and Unsaturated Polyester Composites, PhD Thesis, The University of  
39 Waikato (2009).  
40  
41  
42  
43  
44 [24] Standard Test Method for Tensile Properties of Plastics, ASTM D 638 (2003).  
45  
46  
47 [25] K. L. Pickering, G. W. Beckermann, S. N. Alam, and N. J. Foreman, Optimising  
48 industrial hemp fibre for composites, Composites Part A (Applied Science and  
49 Manufacturing) 38 (2007) 461-468.  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1 [26] A. Stamboulis, C. Baillie, and E. Schulz, Interfacial characterisation of flax fibre-  
2  
3 thermoplastic polymer composites by the pull-out test, *Angewandte Makromolekulare*  
4  
5 *Chemie* 272 (1999) 117-120.  
6

7  
8 [27] M. Todo, P. Sang Dae, K. Arakawa, and M. Koganemaru, Effect of crystallinity  
9  
10 and loading-rate on mode I fracture behavior of poly(lactic acid), *Polymer* 47 (2006)  
11  
12 1357-1363.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

**Figure Captions**

Fig. 1. Specimen preparation schematic for pull-out testing.

Fig. 2. Interfacial shear strength (IFSS) versus embedded length for untreated and alkali treated fibre in PLA.

Fig. 3. PLA crystallinity versus fibre content for untreated and alkali treated fibre composites at different fibre contents.

Fig. 4. Light micrograph of PLA crystallinity in PLA/hemp single fibre composite (scale bar = 100  $\mu\text{m}$ ).

Fig. 5. Light micrographs showing transcrystalline layer of PLA with (a) untreated and (b) treated hemp fibre surfaces (scale bar = 50  $\mu\text{m}$ ).

Fig. 6. Typical load-displacement curves of PLA and composites (PLA/untreated fibre) at (a) 5 mm/min, and (b) 10 mm/min.

Fig. 7. Measurement method of  $P_Q$  from a load-displacement curve.

Fig. 8.  $K_Q$  as a function of loading rate at different fibre contents.

Fig. 9. DSC traces for PLA and composites.

Fig. 10. Relationship between  $K_{Ic}$  and crystallinity for PLA and composites of different fibre contents.

Fig. 11. Light micrographs (side view) of crazing formed in PLA during fracture toughness testing at different loading rates (scale bar = 500 $\mu\text{m}$ ).

Fig. 12. Light micrographs of PLA fracture surfaces tested at loading rates of: (a) 1 mm/min, (b) 5 mm/min, and (c) 10 mm/min.

Fig. 13. Light micrographs showing fracture behaviour of PLA/hemp composites (side view) tested at a loading speed of 5 mm/min at: (a) low magnification and (b) high magnification as a function of fibre content.

1 Fig. 14. Light micrographs showing fracture behaviour of PLA/hemp composites (side  
2 view) tested at a loading speed of 10 mm/min at: (a) low magnification and (b) at high  
3 magnification as a function of fibre content.  
4  
5  
6  
7

8 Fig. 15.  $K_{Ic}$  versus fibre content comparing untreated and alkali treated fibre  
9 composites.  
10  
11  
12

13 Fig. 16. PLA crystallinity for different annealing treatments  
14

15 Fig. 17.  $K_{Ic}$  versus crystallinity isolated from fibre content for alkali treated fibre  
16 composites  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

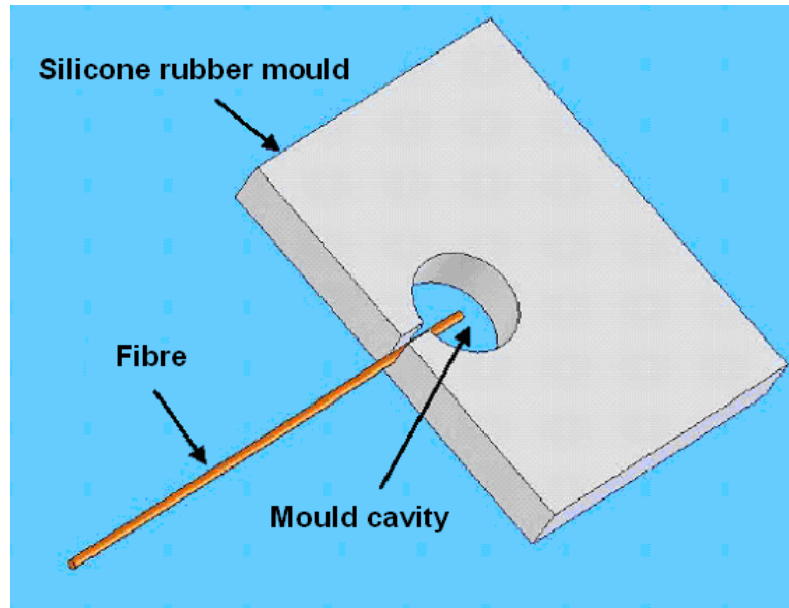


Fig. 1.

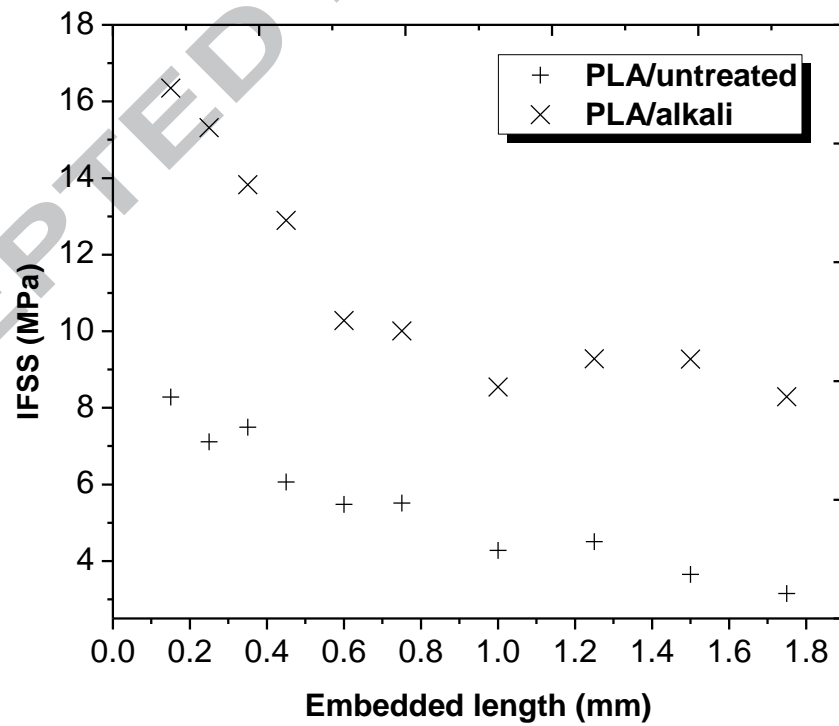


Fig. 2.

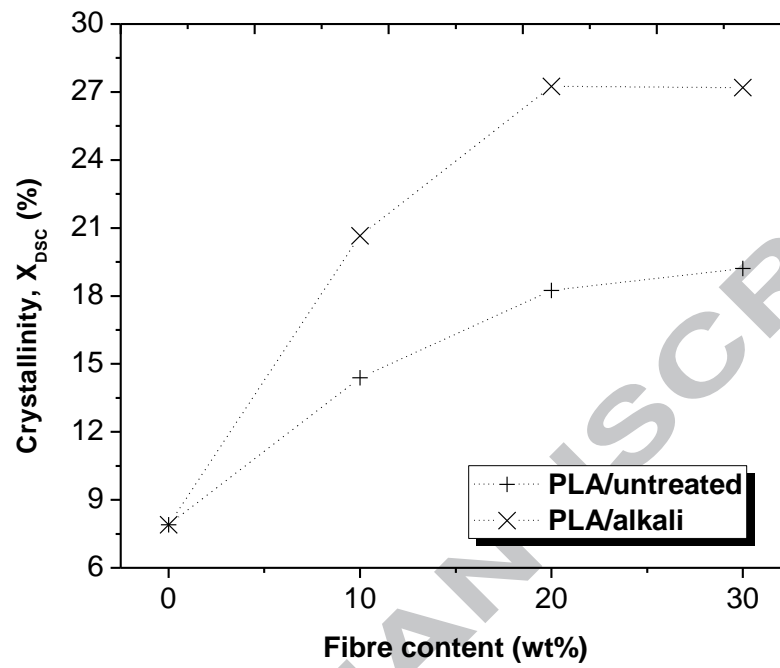


Fig. 3.

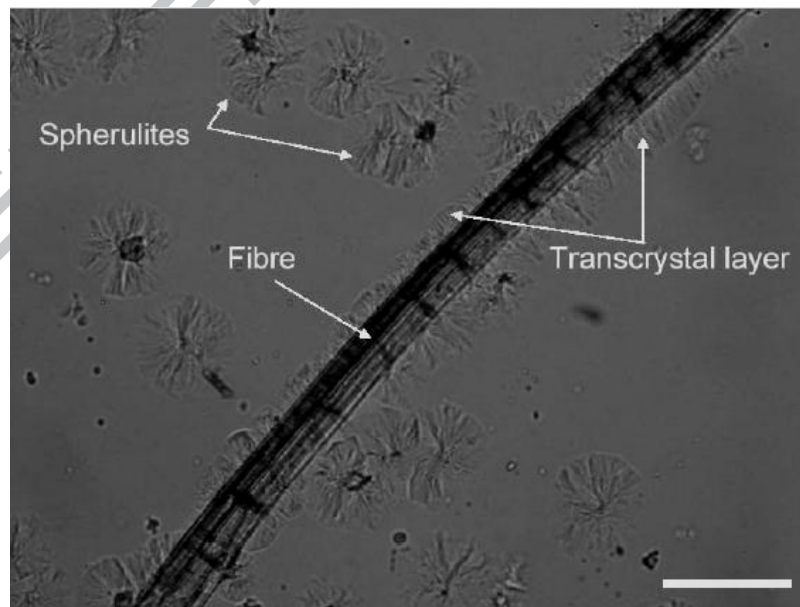


Fig. 4.

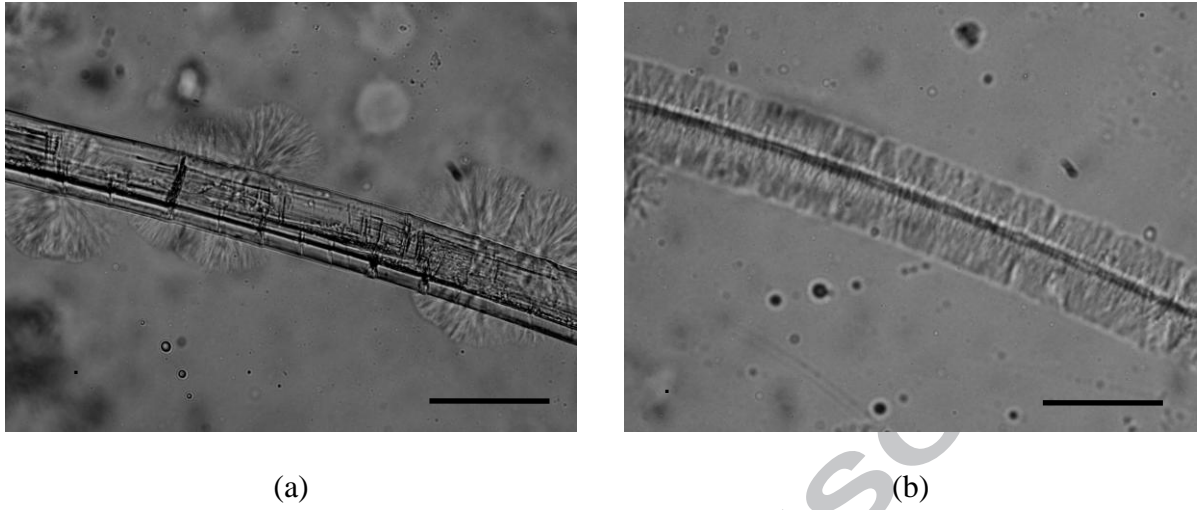


Fig. 5.

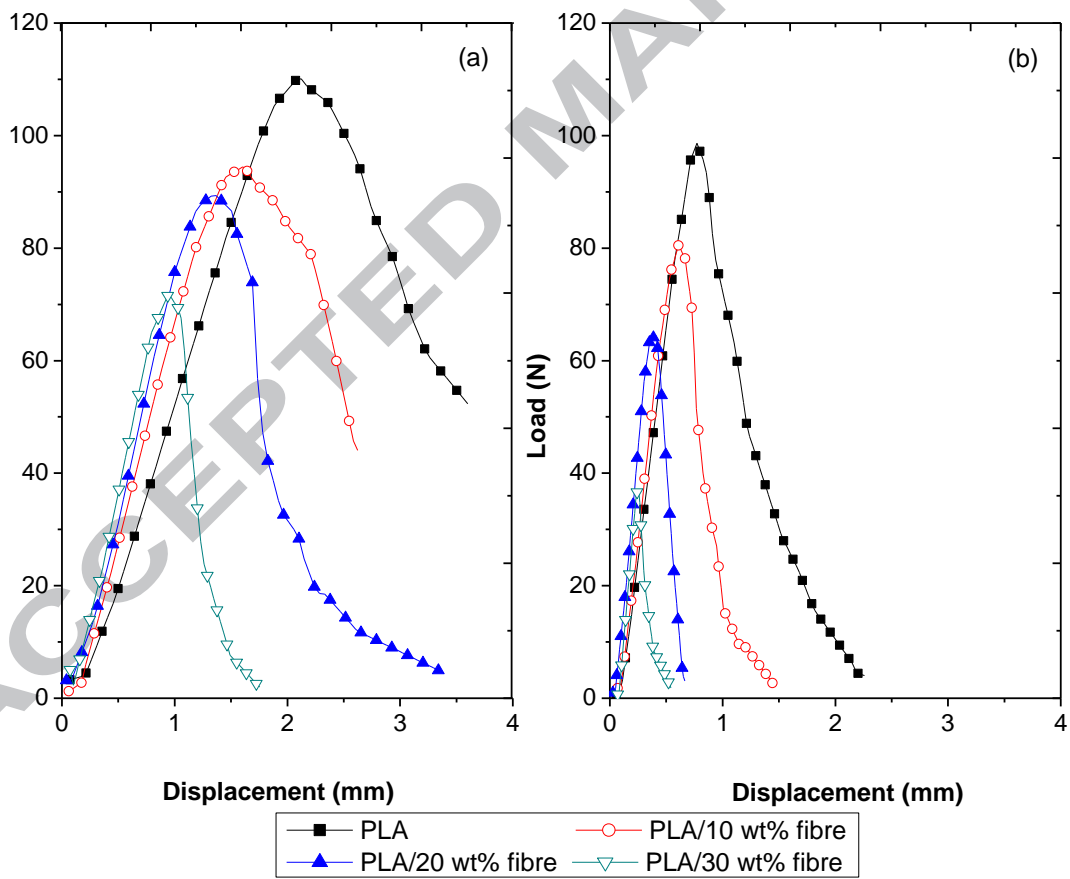


Fig. 6.

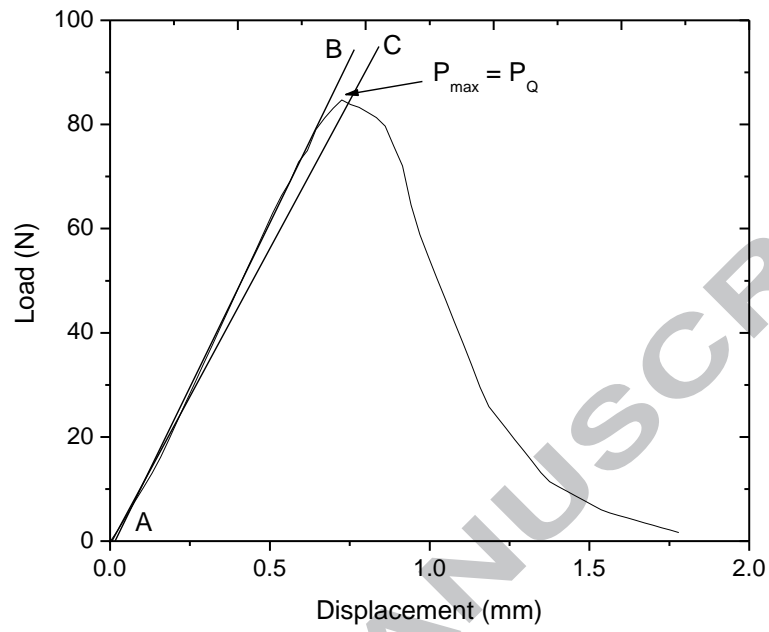


Fig. 7.

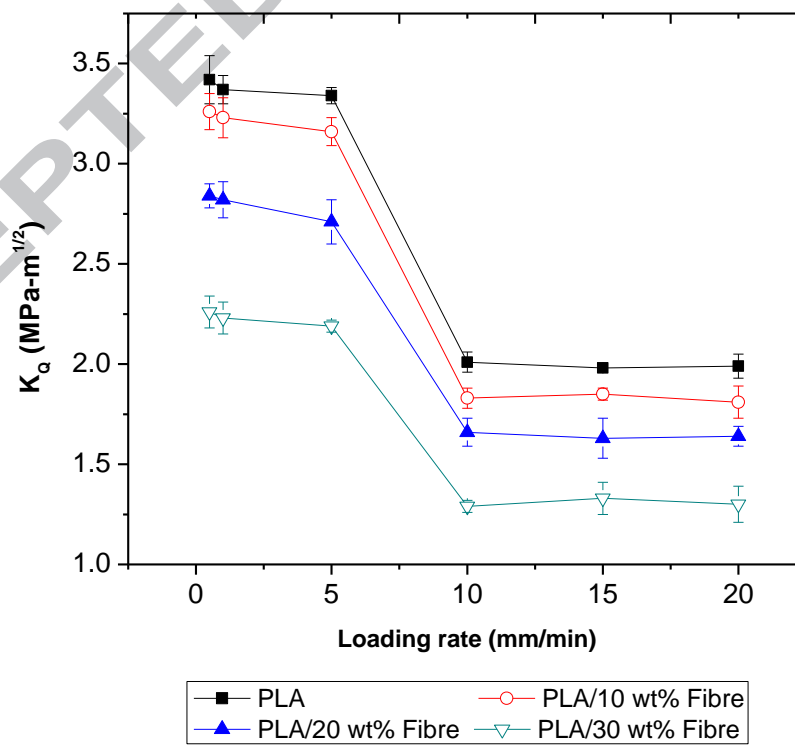


Fig. 8.



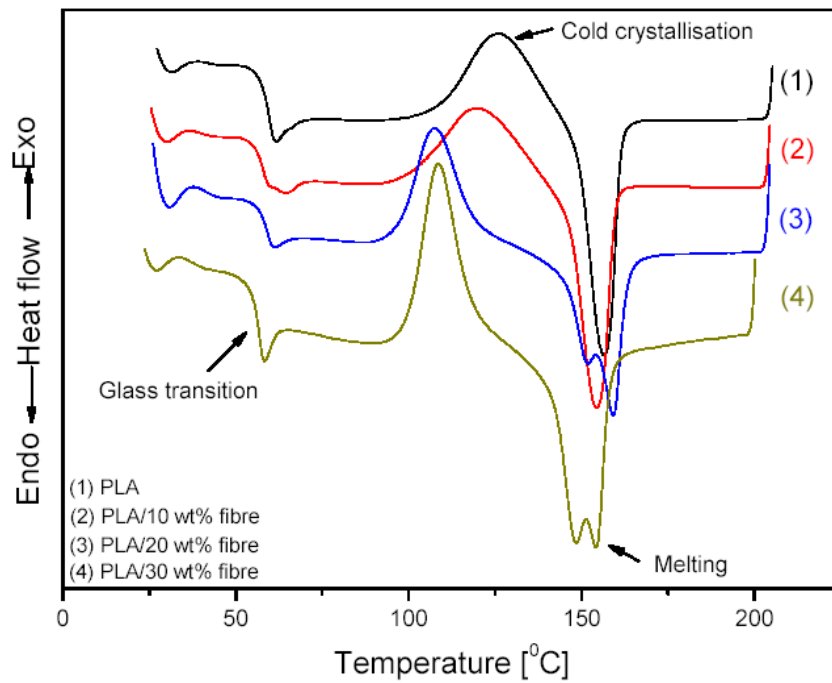


Fig. 9.

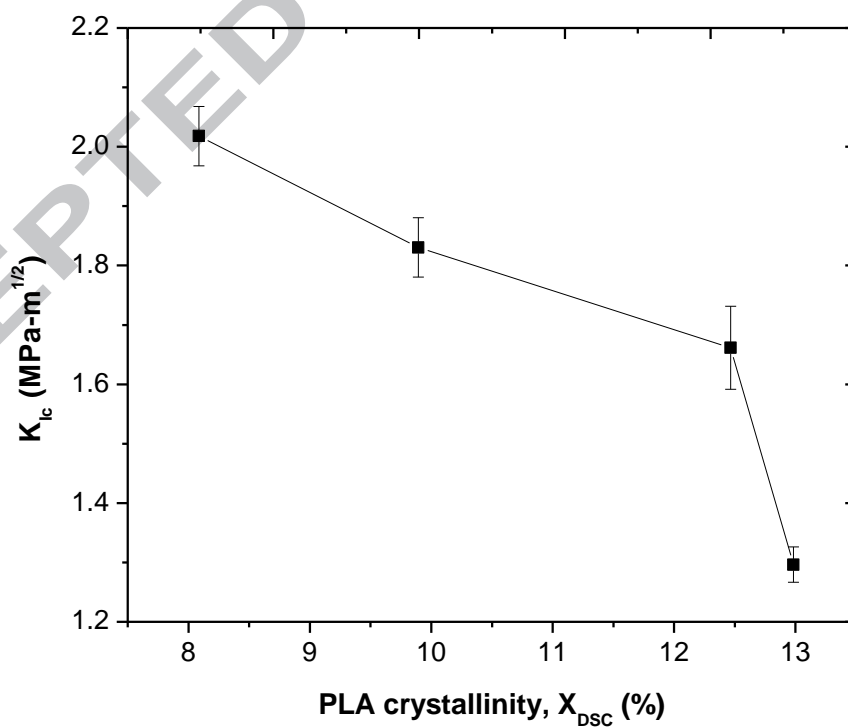


Fig. 10.

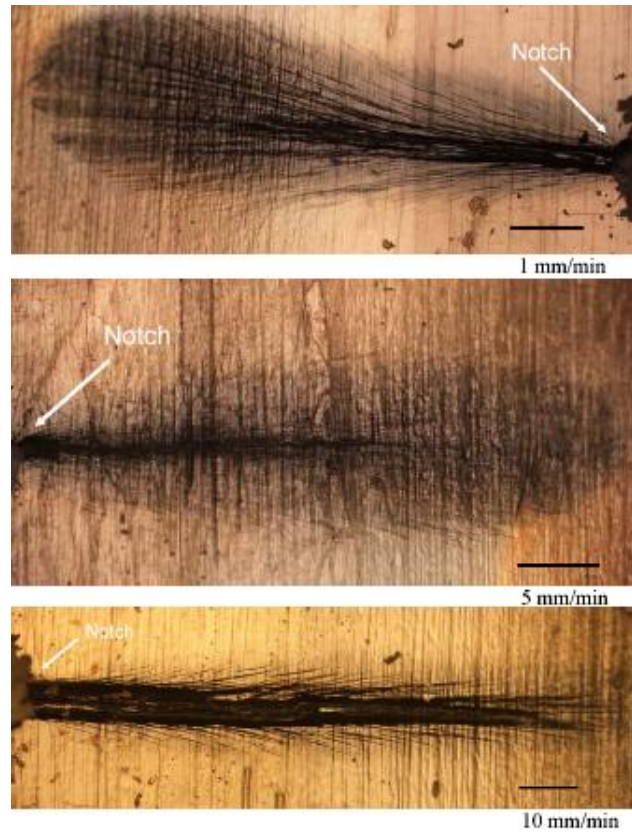


Fig. 11.

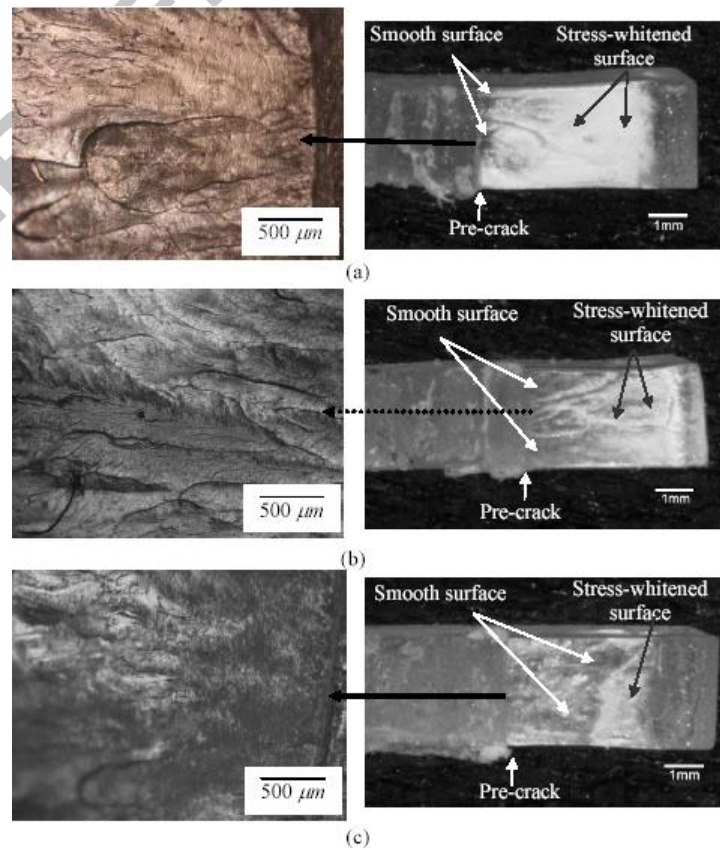


Fig. 12.

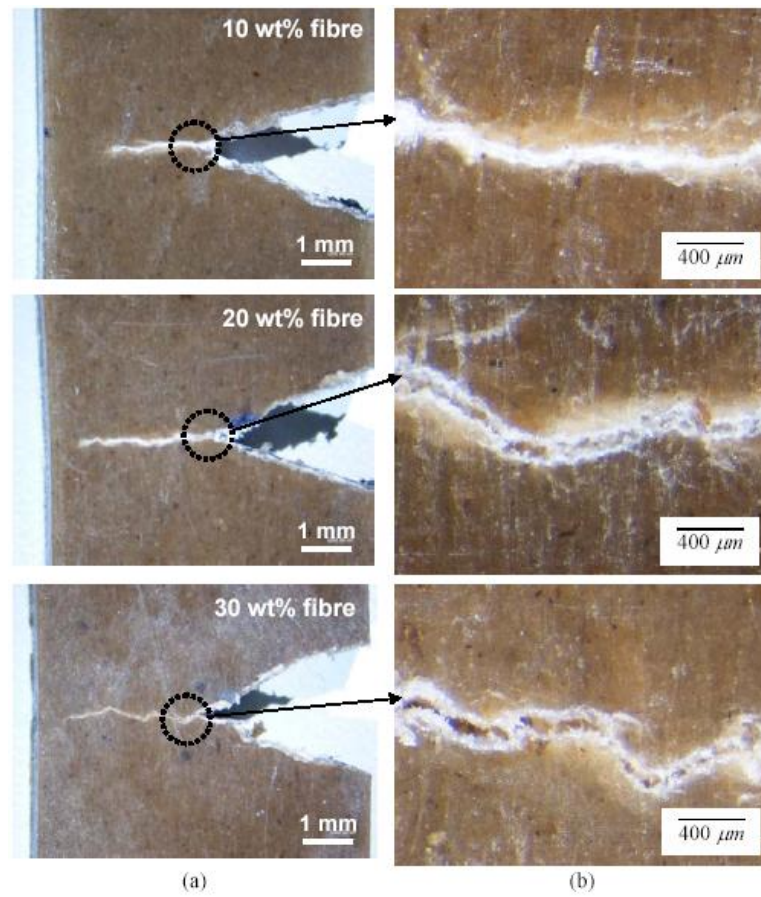


Fig. 13.

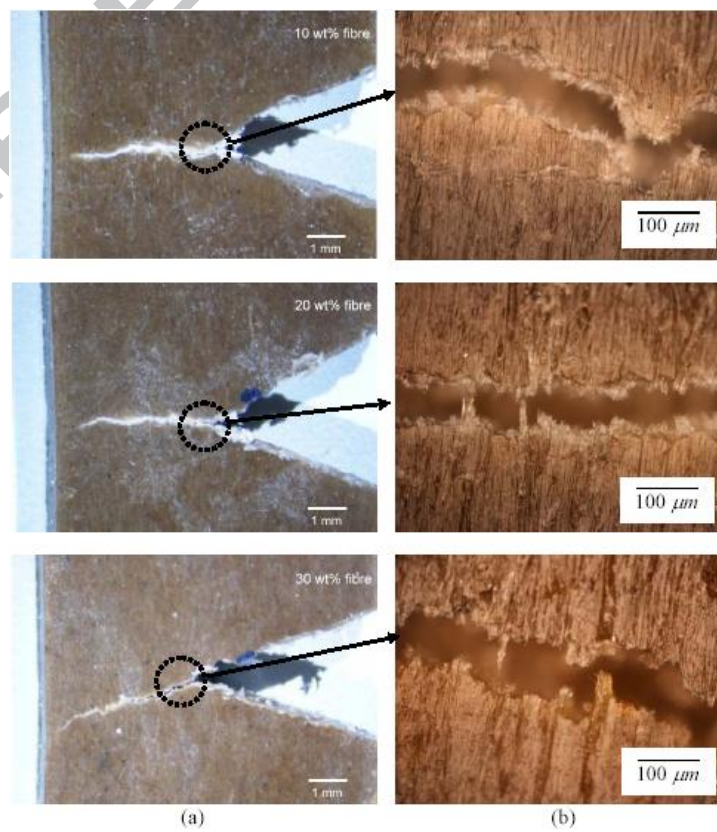


Fig. 14.

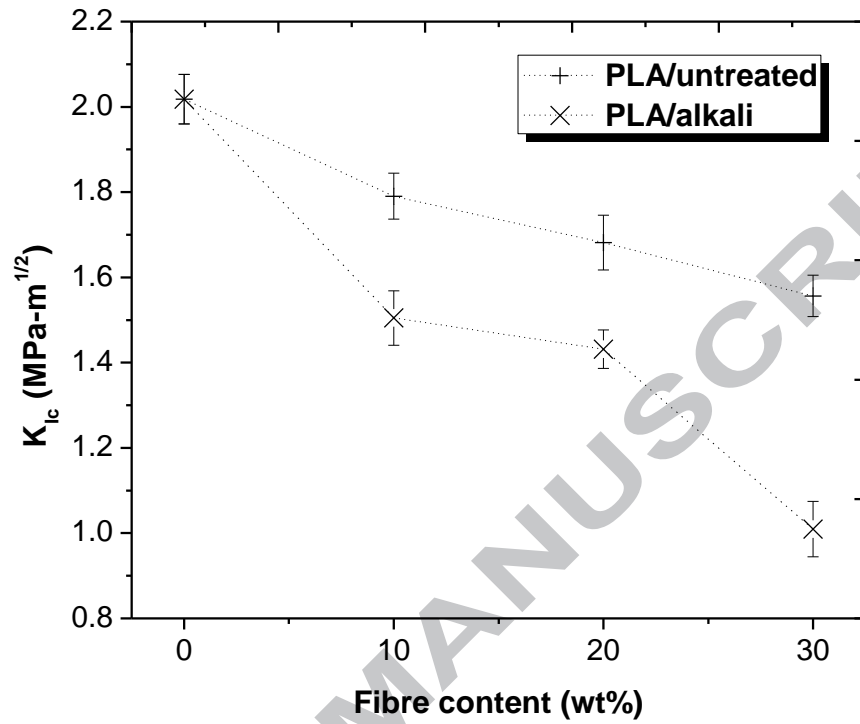


Fig. 15.

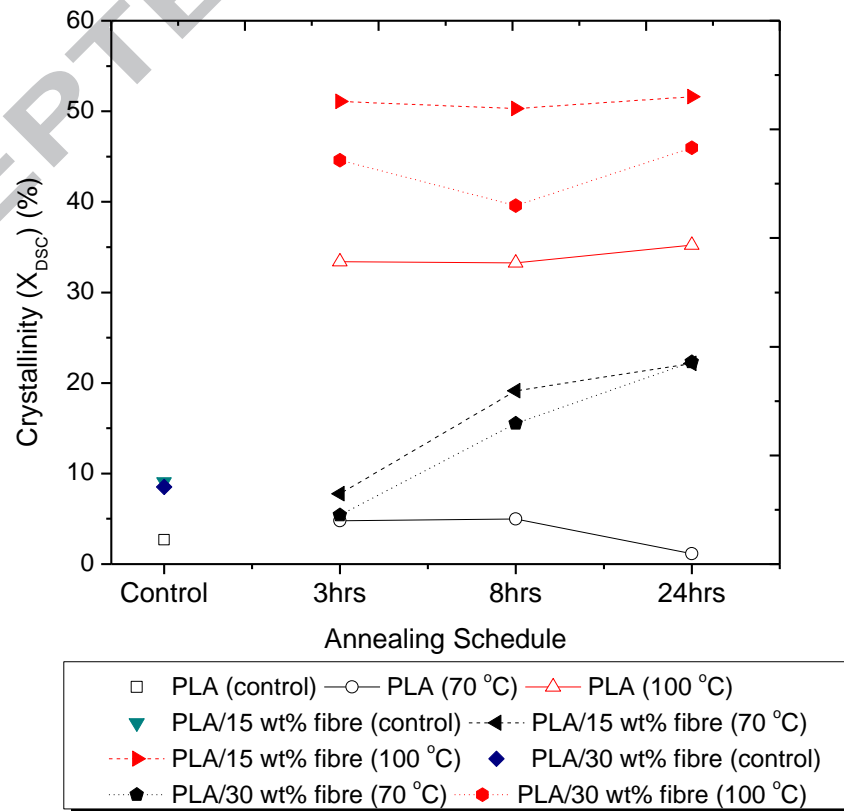


Fig. 16.

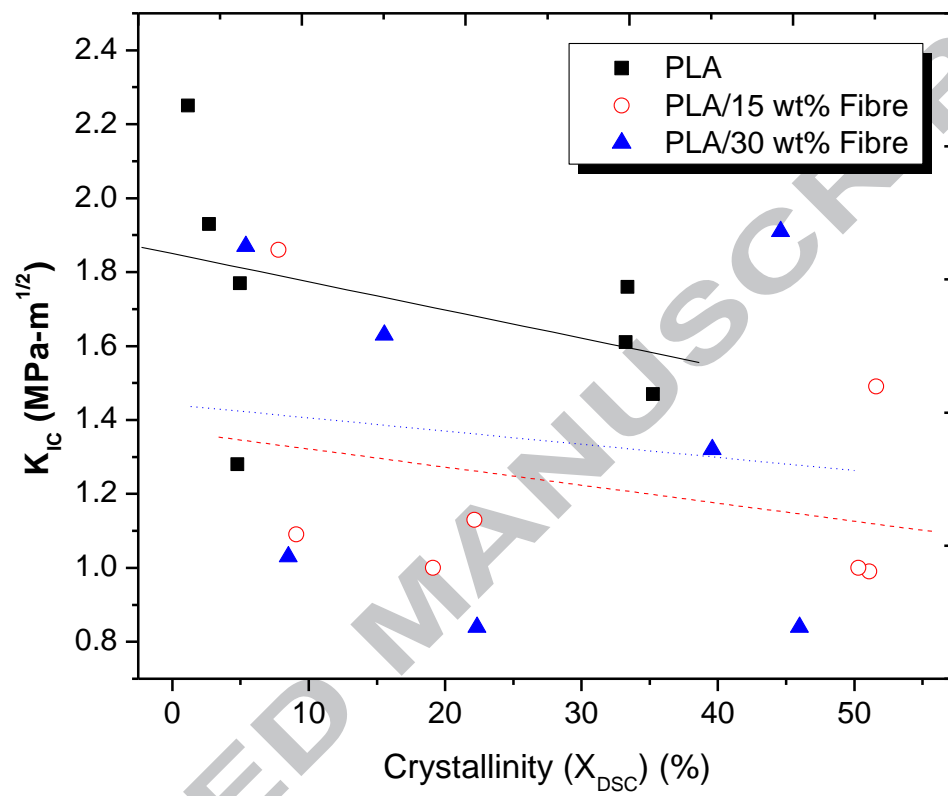


Fig. 17.

Table 1  
Tensile strength of PLA and composites at two different testing speeds and different fibre contents.

Test speed (mm/min)	Fibre content (wt%)	Tensile strength, $\sigma_t$ (MPa)
5	0	50.7 ( $\pm$ 1.21)
	10	52.4 ( $\pm$ 1.17)
	20	59.8 ( $\pm$ 1.97)
	30	65.9 ( $\pm$ 1.10)
10	0	53.9 ( $\pm$ 1.15)
	10	55.7 ( $\pm$ 1.23)
	20	60.4 ( $\pm$ 1.19)
	30	67.2 ( $\pm$ 1.42)